

長谷川研究室 Hasegawa Group

研究テーマ Research Subjects

- 1 低温 STM による特異な超伝導 / トポロジカル物性の探索
Exploration of peculiar superconducting / topological states using low-temperature STM
- 2 マイクロ波導入スピン偏極 STM によるナノスケール磁気共鳴とスピンダイナミクス
Nanoscale detection of magnetic resonances and spin dynamics by microwave-assisted spin-polarized STM
- 3 スピン偏極走査ポテンシオメトリによるスピン流の実空間計測
Real-space distribution of spin currents by spin-polarized scanning tunneling potentiometry
- 4 データ科学支援による高効率局所電子状態計測
Effective collection of local density of states with an assist of data science



教授 長谷川 幸雄
Professor HASEGAWA, Yukio

専攻 Course

工学系物理学

App. Phys., Eng.




助教 土師 将裕
Research Associate
HAZE, Masahiro

走査トンネル顕微鏡 (STM) は、その像を通じて表面の原子構造を明らかにするのみならず、トンネル分光測定によりサブナノ領域での電子状態に関する知見を与え、さらにはスピン偏極 (SP-) STM による局所磁気特性や表面スピン構造を引き出すことができる。

長谷川研究室では、極低温強磁場で動作する STM 装置を用いて、表面超伝導など反転対称性の破れた二次元系での超伝導特性、磁性体との近接効果により誘起される特異な超伝導・トポロジカル状態の観測を試みている。また、SP-STM による磁性薄膜でのスピンスパイラルなど特異な局所磁気構造観察、スピン偏極局所ポテンシオメトリによるスピン流計測、さらにはマイクロ波導入による磁気共鳴検出を通じた局所スピンダイナミクスの研究等も推進しており、プローブ顕微鏡の新たな計測手法を開発することにも取り組んでいる。


Scanning tunneling microscopy (STM) reveals not only atomic structure of surfaces but also electronic states of sub-nanometer areas by tunneling spectroscopy. With a function of spin-polarized (SP-) STM, the microscope also provides local magnetic properties and surface spin structures, and with inelastic tunneling spectroscopy (IETS), various excitation energies can be extracted.

In Hasegawa-lab., by using STMs operated in ultralow temperature and high magnetic field, peculiar local superconducting and topological states that are found e.g. at surfaces, where inversion symmetry is broken, and in the proximity with ferromagnetic and topological materials, have been explored. We have also studied local magnetic properties of nano magnets, peculiar spin-spiral structures, and energy dispersion of surface magnons using SP-STM and SP-IETS. We have also explored unique functionality of the probe microscopy; recent examples include the investigation of local spin dynamics through the detection of magnetic resonances using microwave-assisted SP-STM, spin current detection using SP-scanning tunneling potentiometry, and efficient collection of local density of states based on data-driven science.

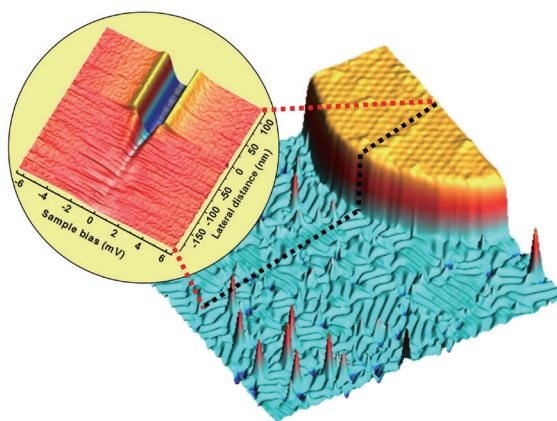

超伝導金属界面での近接効果。単原子層 Pb (水色、金属相) と Pb 薄膜 (黄色、超伝導相) の界面でのトンネル分光から、超伝導特性が界面から約 40nm にわたって染み出している様子が観察される。

Proximity effect at superconductor/metal interface. Tunneling spectra taken around an interface between 1ML-Pb layer on Si (blue, normal metal) and a Pb thin film (yellow, superconductor) indicate the penetration of superconductivity into the metal layer with a decay length of 40 nm.

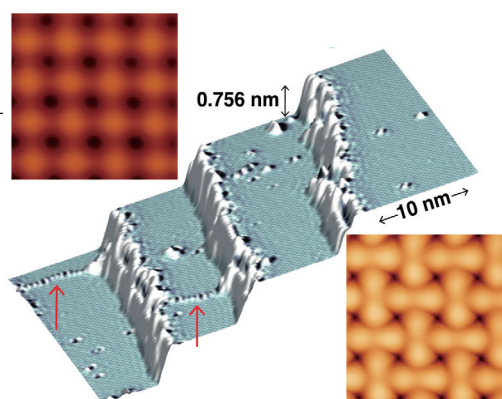

重い電子系物質 CeCoIn₅ で観測された表面軌道秩序。Co 原子が正方配列した面 (中央、左上図) で、探針を近づけて STM 像 (右下図) を撮ると、ダンベル状の d 軌道の秩序配列状態が観察される。

Surface-induced orbital ordered states observed on a heavy-fermion material CeCoIn₅. In STM images taken on a Co-terminated surface in standard conditions, round-shaped Co atoms are observed (center and upper-left images). In STM images taken in closer distances (lower-right) we observed an ordered phase of dumbbell-shaped d-orbitals.

